

# **3rd International Conference Advanced Mechanics: Structure, Materials, Tribology**

---

## **Tribological Comparison of Engineering Polymers in Dry Contact with 6061-T6 Alloy**

AIPCP25-CF-AMSMT2025-00013 | Article

PDF auto-generated using **ReView**





## LICENSE TO PUBLISH AGREEMENT FOR CONFERENCE PROCEEDINGS

This License to Publish must be signed and returned to the Proceedings Editor before the manuscript can be published. If you have questions about how to submit the form, please contact the AIP Publishing Conference Proceedings office (confproc@aip.org). For questions regarding the copyright terms and conditions of this License, please contact AIP Publishing's Office of Rights and Permissions, 1305 Walt Whitman Road, Suite 300, Melville, NY 11747-4300 USA; Phone 516-576-2268; Email: [rights@aip.org](mailto:rights@aip.org).

Article Title ("Work"): Tribological Comparison of Engineering Polymers in Dry Contact with 6061-T6 Alloy

(Please indicate the final title of the Work. Any substantive changes made to the title after acceptance of the Work may require the completion of a new agreement.)

All Author(s): 1-1 Safa Unal

2-1 H. Abdullah Tasdemir

(Please list all the authors' names in order as they will appear in the Work. All listed authors must be fully deserving of authorship and no such authors should be omitted. For large groups of authors, attach a separate list to this form.)

Title of Conference: 3rd International Conference Advanced Mechanics: Structure, Material, Tribology

Name(s) of Editor(s): Valentin L. Popov and Asktor 2. Khasanov

All Copyright Owner(s), if not Author(s):

(Please list all copyright owner(s) by name. In the case of a Work Made for Hire, the employer(s) or commissioning party(ies) are the copyright owner(s). For large groups of copyright owners, attach a separate list to this form.)

Copyright Ownership and Grant of Rights

For the purposes of this License, the "Work" consists of all content within the article itself and made available as part of the article, including but not limited to the abstract, tables, figures, graphs, images, and multimedia files, as well as any subsequent errata. "Supplementary Material" consists of material that is associated with the article but linked to or accessed separately (available electronically only), including but not limited to data sets and any additional files.

This Agreement is an Exclusive License to Publish not a Transfer of Copyright. Copyright to the Work remains with the Author(s) or, in the case of a Work Made for Hire, with the Author(s)' employer(s). AIP Publishing LLC shall own and have the right to register in its name the copyright to the proceedings issue or any other collective work in which the Work is included. Any rights granted under this License are contingent upon acceptance of the Work for publication by AIP Publishing. If for any reason and at its own discretion AIP Publishing decides not to publish the Work, this License is considered void.

Each Copyright Owner hereby grants to AIP Publishing LLC the following irrevocable rights for the full term of United States and foreign copyrights (including any extensions):

1. The exclusive right and license to publish, reproduce, distribute, transmit, display, store, translate, edit, adapt, and create derivative works from the Work (in whole or in part) throughout the world in all formats and media whether now known or later developed, and the nonexclusive right and license to do the same with the Supplementary Material.
2. The right for AIP Publishing to freely transfer and/or sublicense any or all of the exclusive rights listed in #1 above. Sublicensing includes the right to authorize requests for reuse of the Work by third parties.
3. The right for AIP Publishing to take whatever steps it considers necessary to protect and enforce, at its own expense, the exclusive rights granted herein against third parties.

Author Rights and Permitted Uses

Subject to the rights herein granted to AIP Publishing, each Copyright Owner retains ownership of copyright and all other proprietary rights such as patent rights in the Work.

Each Copyright Owner retains the following nonexclusive rights to use the Work, without obtaining permission from AIP Publishing, in keeping with professional publication ethics and provided clear credit is given to its first publication in an AIP Publishing proceeding. Any reuse must include a full credit line acknowledging AIP Publishing's publication and a link to the Version of Record (VOR) on AIP Publishing's site.

Each Copyright Owner may:

1. Reprint portions of the Work (excerpts, figures, tables) in future works created by the Author, in keeping with professional publication ethics.
2. Post the Accepted Manuscript (AM) to their personal web page or their employer's web page immediately after acceptance by AIP Publishing.
3. Deposit the AM in an institutional or funder-designated repository immediately after acceptance by AIP Publishing.

4. Use the AM for posting within scientific collaboration networks (SCNs). For a detailed description of our policy on posting to SCNs, please see our Web Posting Guidelines (<https://publishing.aip.org/authors/web-posting-guidelines>).
5. Reprint the Version of Record (VOR) in print collections written by the Author, or in the Author's thesis or dissertation. It is understood and agreed that the thesis or dissertation may be made available electronically on the university's site or in its repository and that copies may be offered for sale on demand.
6. Reproduce copies of the VOR for courses taught by the Author or offered at the institution where the Author is employed, provided no fee is charged for access to the Work.
7. Use the VOR for internal training and noncommercial business purposes by the Author's employer.
8. Use the VOR in oral presentations made by the Author, such as at conferences, meetings, seminars, etc., provided those receiving copies are informed that they may not further copy or distribute the Work.
9. Distribute the VOR to colleagues for noncommercial scholarly use, provided those receiving copies are informed that they may not further copy or distribute the Work.
10. Post the VOR to their personal web page or their employer's web page 12 months after publication by AIP Publishing.
11. Deposit the VOR in an institutional or funder-designated repository 12 months after publication by AIP Publishing.
12. Update a prior posting with the VOR on a noncommercial server such as arXiv, 12 months after publication by AIP Publishing.



Author Warranties

Each Author and Copyright Owner represents and warrants to AIP Publishing the following:

1. The Work is the original independent creation of each Author and does not infringe any copyright or violate any other right of any third party.
2. The Work has not been previously published and is not being considered for publication elsewhere in any form, except as a preprint on a noncommercial server such as arXiv, or in a thesis or dissertation.
3. Written permission has been obtained for any material used from other sources and copies of the permission grants have been supplied to AIP Publishing to be included in the manuscript file.
4. All third-party material for which permission has been obtained has been properly credited within the manuscript.
5. In the event that the Author is subject to university open access policies or other institutional restrictions that conflict with any of the rights or provisions of this License, such Author has obtained the necessary waiver from his or her university or institution.

This License must be signed by the Author(s) and, in the case of a Work Made for Hire, also by the Copyright Owners. One Author/Copyright Owner may sign on behalf of all the contributors/owners only if they all have authorized the signing, approved of the License, and agreed to be bound by it. The signing Author and, in the case of a Work Made for Hire, the signing Copyright Owner warrants that he/she/it has full authority to enter into this License and to make the grants this License contains.

1. The Author must please sign here (except if an Author is a U.S. Government employee, then please sign under #3 below): Tribological Comparison of Engineering Polymers in Dry Contact with 6061-T6 Alloy

 Author(s) Signature  Print Name  Date 15.08.25

2. The Copyright Owner (if different from the Author) must please sign here:

Name of Copyright Owner	Authorized Signature and Title	Date
-------------------------	--------------------------------	------

3. If an Author is a U.S. Government employee, such Author must please sign below. The signing Author certifies that the Work was written as part of his/her official duties and is therefore not eligible for copyright protection in the United States.

Name of U.S. Government Institution (e.g., Naval Research Laboratory, NIST)

Author Signature	Print Name	Date
------------------	------------	------

PLEASE NOTE: NATIONAL LABORATORIES THAT ARE SPONSORED BY U.S. GOVERNMENT AGENCIES BUT ARE INDEPENDENTLY RUN ARE NOT CONSIDERED GOVERNMENT INSTITUTIONS. (For example, Argonne, Brookhaven, Lawrence Livermore, Sandia, and others.) Authors at these types of institutions should sign under #1 or #2 above.

If the Work was authored under a U.S. Government contract, and the U.S. Government wishes to retain for itself and others acting on its behalf, a paid-up, nonexclusive, irrevocable, worldwide license in the Work to reproduce, prepare derivative works from, distribute copies to the public, perform publicly, and display publicly, by or on behalf of the Government, please check the box below and add the relevant Contract numbers.

Contract #(s) \_\_\_\_\_ [1.16.1]

## LICENSE TERMS DEFINED

**Accepted Manuscript (AM):** The final version of an author's manuscript that has been accepted for publication and incorporates all the editorial changes made to the manuscript after submission and peer review. The AM does not yet reflect any of the publisher's enhancements to the work such as copyediting, pagination, and other standard formatting.

**arXiv:** An electronic archive and distribution server for research article preprints in the fields of physics, mathematics, computer science, quantitative biology, quantitative finance, and statistics, which is owned and operated by Cornell University, <http://arxiv.org/>.

**Commercial and noncommercial scholarly use:** *Noncommercial* scholarly uses are those that further the research process for authors and researchers on an individual basis for their own personal purposes. They are author-to-author interactions meant for the exchange of ideas. *Commercial* uses fall outside the author-to-author exchange and include but are not limited to the copying or distribution of an article, either in hard copy form or electronically, for resale or licensing to a third party; posting of the AM or VOR of an article by a site or service where an access fee is charged or which is supported by commercial paid advertising or sponsorship; use by a for-profit entity for any type of promotional purpose. Commercial uses require the permission of AIP Publishing.

**Embargo period:** The period of time during which free access to the full text of an article is delayed.

**Employer's web page:** A web page on an employer's site that highlights the accomplishments and research interests of the company's employees, which usually includes their publications. (See also: Personal web page and Scholarly Collaboration Network).

**Exclusive License to Publish:** An exclusive license to publish is a written agreement in which the copyright owner gives the publisher exclusivity over certain inherent rights associated with the copyright in the work. Those rights include the right to reproduce the work, to distribute copies of the work, to perform and display the work publicly, and to authorize others to do the same. The publisher does not hold the copyright to the work, which continues to reside with the author. The terms of the AIP Publishing License to Publish encourage authors to make full use of their work and help them to comply with requirements imposed by employers, institutions, and funders.

**Full Credit Line:** AIP Publishing's preferred format for a credit line is as follows (you will need to insert the specific citation information in place of the capital letters): "Reproduced from [FULL CITATION], with the permission of AIP Publishing." A FULL CITATION would appear as: Journal abbreviation, volume number, article ID number or page number (year). For example: Appl. Phys. Lett. 107, 021102 (2015).

**Institutional repository:** A university or research institution's digital collection of articles that have been authored by its staff and which are usually made publicly accessible. As authors are encouraged and sometimes required to include their published articles in their institution's repository, the majority of publishers allow for deposit of the Accepted Manuscript for this purpose. AIP Publishing also allows for the VOR to be deposited 12 months after publication of the Work.

**Journal editorial office:** The contact point for authors concerning matters related to the publication of their manuscripts. Contact information for the journal editorial offices may be found on the journal websites under the "About" tab.

**Linking to the Version of Record (VOR):** To create a link to your article in an AIP Publishing journal or proceedings, you need to know the CrossRef digital object identifier (doi). You can find the doi on the article's abstract page. For instructions on linking, please refer to our Web Posting Guidelines at <https://publishing.aip.org/authors/web-posting-guidelines>.

**National Laboratories:** National laboratories are sponsored and funded by the U.S. Government but have independent nonprofit affiliations and employ private sector resources. These institutions are classified as Federally Funded Research and Development Centers (FFRDCs). Authors working at FFRDCs are not

considered U.S. Government employees for the purposes of copyright. The Master Government List of FFRDCs may be found at <http://www.nsf.gov/statistics/ffrdcls/>.

**Personal web page:** A web page that is hosted by the author or the author's institution and is dedicated to the author's personal research interests and publication history. An author's profile page on a social media site or scholarly collaboration network site is *not* considered a personal web page. (See also: Scholarly Collaboration Network; Employer's web page).

**Peer X-Press:** A web-based manuscript submission system by which authors submit their manuscripts to AIP Publishing for publication, communicate with the editorial offices, and track the status of their submissions. The Peer X-Press system provides a fully electronic means of completing the License to Publish. A hard copy of the Agreement will be supplied by the editorial office if the author is unable to complete the electronic version of the form. (Conference Proceedings authors will continue to submit their manuscripts and forms directly to the Conference Editors.)

**Preprint:** A version of an author's manuscript intended for publication but that has not been peer reviewed and does not reflect any editorial input or publisher enhancements.

**Professional Publication Ethics:** AIP Publishing provides information on what it expects from authors in its "Statement of ethics and responsibilities of authors submitting to AIP Publishing journals" (<http://publishing.aip.org/authors/ethics>). AIP Publishing is also a member of the Committee on Publication Ethics (COPE) (<http://publicationethics.org/>), which provides numerous resources and guidelines for authors, editors, and publishers with regard to ethical standards and accepted practices in scientific publishing.

**Scholarly Collaboration Network (SCN):** Professional networking sites that facilitate collaboration among researchers as well as the sharing of data, results, and publications. SCNs include sites such as Academia.edu, ResearchGate, and Mendeley, among others.

**Supplementary Material:** Related material that has been judged by peer review as being relevant to the understanding of the article but that may be too lengthy or of too limited interest for inclusion in the article itself. Supplementary Material may include data tables or sets, appendixes, movie or audio clips, or other multimedia files.

**U.S. Government employees:** Authors working at Government organizations who author works as part of their official duties and who are not able to license rights to the Work, since no copyright exists. Government works are in the public domain within the United States.

**Version of Record (VOR):** The final published version of the article as it appears in the printed journal/proceedings or on the Scitation website. It incorporates all editorial input, is formatted in the publisher's standard style, and is usually viewed in PDF form.

**Waiver:** A request made to a university or institution to exempt an article from its open-access policy requirements. For example, a conflict will exist with any policy that requires the author to grant a nonexclusive license to the university or institution that enables it to license the Work to others. In all such cases, the Author must obtain a waiver, which shall be included in the manuscript file.

**Work:** The "Work" is considered all the material that comprises the article, including but not limited to the abstract, tables, figures, images, multimedia files that are directly embedded within the text, and the text itself. The Work does not include the Supplementary Material (see Supplementary Material above).

**Work Made for Hire:** Under copyright law, a work prepared by an employee within the scope of employment, or a work that has been specially ordered or commissioned for which the parties have agreed in writing to consider as a Work Made for Hire. The hiring party or employer is considered the author and owner of the copyright, not the person who creates the work.

# Tribological Comparison of Engineering Polymers in Dry Contact With 6061-T6 Alloy

Safa Unal<sup>1, a)</sup> and Haci Abdullah Tasdemir<sup>1, b)</sup>

<sup>1</sup>Department of Mechanical Engineering, Istanbul Technical University, Istanbul, Turkiye

<sup>a)</sup> Corresponding author: unalsa23@itu.edu.tr  
<sup>b)</sup> tasdemirh@itu.edu.tr

**Abstract.** In this study, four widely used high-performance polymers polyoxymethylene copolymer (POM-C), polytetrafluoroethylene (PTFE), polyamide-6 (PA-6), and cast polyamide-6 (PA-6G) were systematically evaluated under dry sliding conditions when paired with 6061-T6 aluminum alloy as the tribological counterpart. Frictional properties were examined through tribometer measurements to determine the average coefficients of friction, while wear rates were analyzed using the optical profilometry method. The results showed that PA-6G exhibited the best overall tribological performance, having the lowest coefficient of friction (0.16) and the lowest wear rate (1.87%). PA-6 demonstrated the second-best performance with a friction coefficient of 0.22 and an approximate wear rate of 7.87%. Although PTFE exhibited a relatively low coefficient of friction (0.28), it showed a considerably high wear rate (22.10%). POM-C, compared to the other tested polymer samples, presented the highest coefficient of friction (0.34) and a high wear rate (25.84%), indicating poor tribological performance. The aluminum counterpart material (6061-T6) exhibited the highest wear rate of 42.32%. In this study, POM-C, PTFE, PA-6, and PA-6G polymers, which have been frequently reported in recent literature, were comparatively evaluated under identical test conditions to contribute to both industrial applications and the academic community.


## INTRODUCTION

High-performance polymers such as polyoxymethylene copolymer (POM-C), polytetrafluoroethylene (PTFE), cast polyamide-6 (PA-6G), and polyamide-6 (PA-6) are widely used in fields such as aerospace, automotive, and mechanical engineering due to their numerous advantageous properties, including low friction coefficients, high wear resistance, and long service life in operational systems. In contemporary engineering applications, these materials have increasingly become preferred alternatives to conventional engineering components owing to their durability, ease of assembly and maintenance, and lightweight characteristics [1–4]. Therefore, the tribological evaluation of frequently utilized polymers such as POM-C, PTFE, PA-6G, and PA-6 is highly important both for industry particularly for R&D engineers involved in material selection during the design stage and for academia, as it contributes to the literature and provides insight into new solutions. However, a review of the literature reveals that although these polymers have been widely reported as commonly used materials, they have often been examined separately under different testing conditions. Consequently, a lack of comparability has emerged in the material selection and academic assessment processes [5–17]. In this context, the present study conducted tribological evaluations of high-performance polymers recently reported to be extensively used in industry under identical test conditions, and the obtained findings were systematically analyzed.

## EXPERIMENTAL


In this study, all test specimens were meticulously prepared following the geometric and material specifications prescribed by the ASTM G133 standard. Pin samples, fabricated from 6061-T6 aluminum alloy, are detailed in terms of dimensions in Fig. 1a. The counterpart materials against which these pins were slid during tribological testing included PTFE, PA-6G, POM-C, PA-6, and 6061-T6 aluminum alloy, with their shapes and dimensions illustrated in


Fig. 1b. These commercially obtained materials are well-established for their widespread application in various industrial settings. The hardness and surface roughness ( $R_a$ ) values of each material, measured using an optical profilometer, are provided in Fig. 2. Throughout the experiments, the pin specimens were reciprocally slid against the selected counterface materials to simulate realistic frictional interactions under controlled conditions.

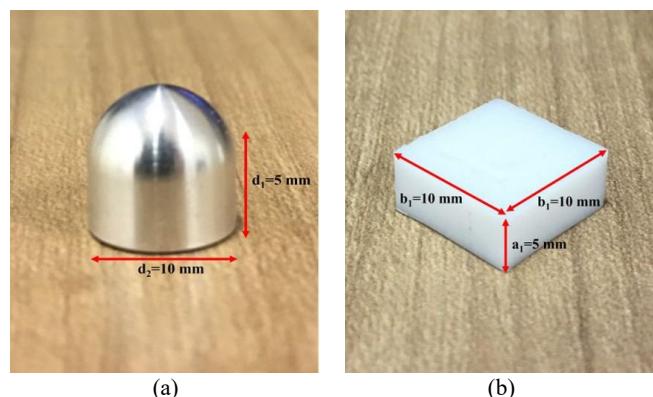

**FIGURE 1.** Specimen geometries used in this study: (a) cylindrical pin specimen; (b) rectangular prism-shaped counterface specimen.


Tribological tests were performed using a tribometer equipped with a linear reciprocating motion module (Fig. 3). Specimen surfaces were meticulously prepared both before and after each test. This preparation protocol aimed to minimize the influence of potential contaminants and surface impurities on the test outcomes. Initially, surface oils and particulate residues were removed using benzene cleaning, followed by an ultrasonic bath treatment with acetone to eliminate any remaining contaminants completely. This two-step cleaning procedure ensured that the specimen surfaces were thoroughly free of impurities, enabling reliable evaluation of tribological performance. Unless otherwise specified, this standardized cleaning protocol was consistently applied throughout all experiments.

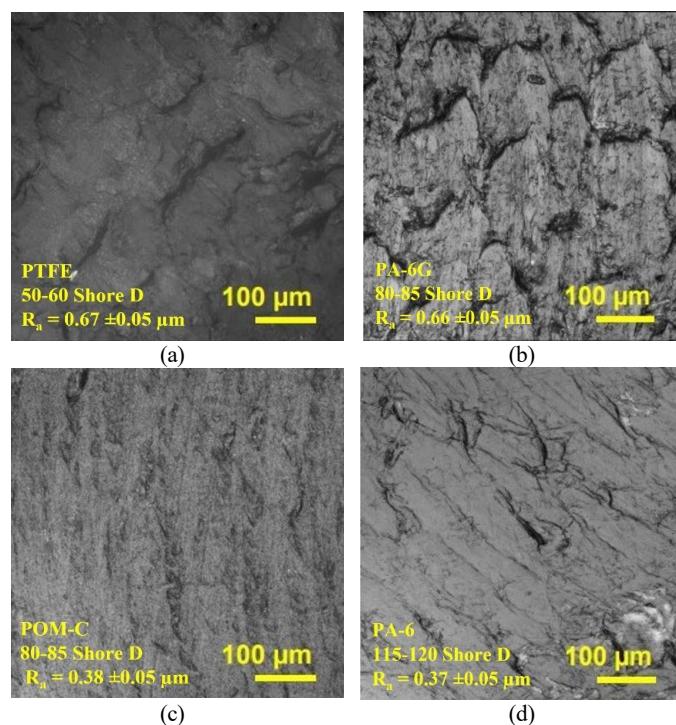

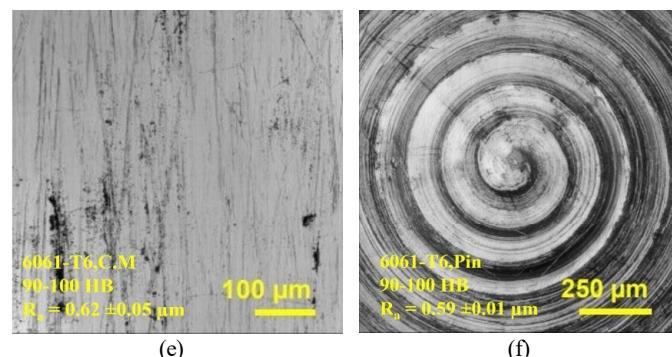

**FIGURE 2.** Optical profilometer images and corresponding hardness and surface roughness ( $R_a$ ) values of the tested materials: (a) PTFE (counter material), (b) PA-6G (counter material), (c) POM-C (counter material), (d) PA-6 (counter material), (e) 6061-T6 aluminum alloy (counter material), and (f) 6061-T6 aluminum alloy (pin material).

Tribological tests were carried out employing a reciprocating setup where a ball slid against a flat specimen. During the experiments, a constant normal load of 5 N was applied, and the reciprocating motion was driven at a frequency of 5 Hz, resulting in an estimated initial peak Hertzian contact pressure of approximately 107 MPa. The tests were performed at a steady sliding speed of 0.06 meters per second. Each test lasted for 1833 seconds, corresponding to a total sliding distance of 110 meters. To isolate the inherent tribological properties of the materials, all tests were conducted under dry conditions without lubrication. Environmental factors were strictly controlled, maintaining an ambient temperature of 24 °C and relative humidity at 39%. Each experimental condition was repeated four times to ensure the reliability and reproducibility of the results. Following the tests, wear tracks on the samples were examined using a Zeiss optical profilometer, providing detailed, high-resolution images of the wear morphology.

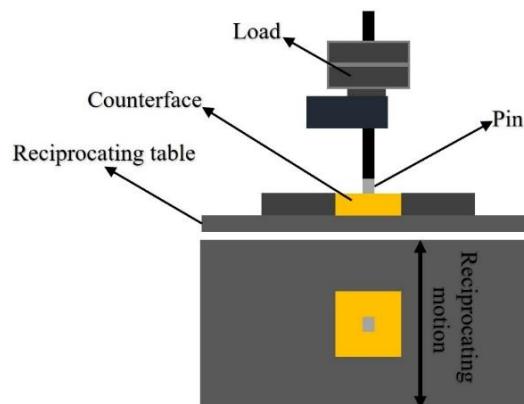


**FIGURE 3.** Tribometer setup employed in the tribological experiments, featuring a linear reciprocating motion module.

## RESULT AND DISCUSSION

Figure 4a presents the steady-state coefficients of friction (COF) for PTFE, PA-6G, POM-C, PA-6, and 6061-T6, obtained from dry sliding tests against a 6061-T6 aluminum pin. In addition, Fig. 4b illustrates the variation in friction force over the course of the experiments, whereas Fig. 4c presents the mean force values together with their associated standard errors. The steady-state stage, defined as the period in which the interfacial conditions attained dynamic equilibrium [18], was marked by stable friction levels across all materials, with negligible oscillations. A distinct ranking in tribological performance emerged: PA-6G exhibited the lowest COF (~0.16) and mean friction force (~0.79 N), maintaining outstanding stability from the beginning to the end of the test. This behavior can be attributed to its

semi-crystalline architecture and inherent lubricating ability, which mitigate adhesive junction formation and reduce frictional resistance [19–22]. PA-6 followed, with a COF of ~0.22 and a mean force of ~1.10 N, consistent with prior findings [23], where its elasticity and adaptive contact behavior were shown to distribute stresses more evenly and promote friction stability under unlubricated conditions [21]. PTFE displayed intermediate performance, with a COF of ~0.28 and mean force of ~1.41 N. Despite its low surface energy and lamellar structure, these values exceeded those of PA-6 and PA-6G, possibly due to limited transfer film formation or load-bearing constraints under dry contact [24]. Metallic 6061-T6 yielded a COF near 0.33 and an average force of ~1.65 N, exhibiting typical dry-sliding metallic trends with minimal temporal variation. POM-C recorded the highest COF (~0.34) and friction force (~1.69 N), reaching stability shortly after a brief running-in phase, in alignment with previous results for steel-based counterparts [25,26].

Wear analysis, obtained after tribometer testing via a Zeiss Smartproof 5 optical profilometer, further corroborates the frictional findings (Fig. 4d). Wear volumes measured on the counterpart surfaces were converted into wear rates, revealing that the 6061-T6 aluminum counterpart suffered the highest wear contribution, accounting for 42.32% of the total measured wear. In contrast, PA-6G demonstrated exceptional wear resistance, with only 1.87% of the total wear volume. The remaining materials POM-C, PTFE, and PA-6 contributed 25.84%, 22.10%, and 7.87%, respectively, underscoring the substantial variations in wear performance among the tested specimens. Taken together, these results indicate that microstructural characteristics, surface compliance, and surface energy jointly govern long-term dry-sliding tribological behavior. In practical terms, PA-6G and PA-6 emerge as strong candidates for lubrication-free applications, whereas POM-C and 6061-T6 would likely benefit from surface engineering or lubrication strategies to mitigate friction and wear-related energy losses.

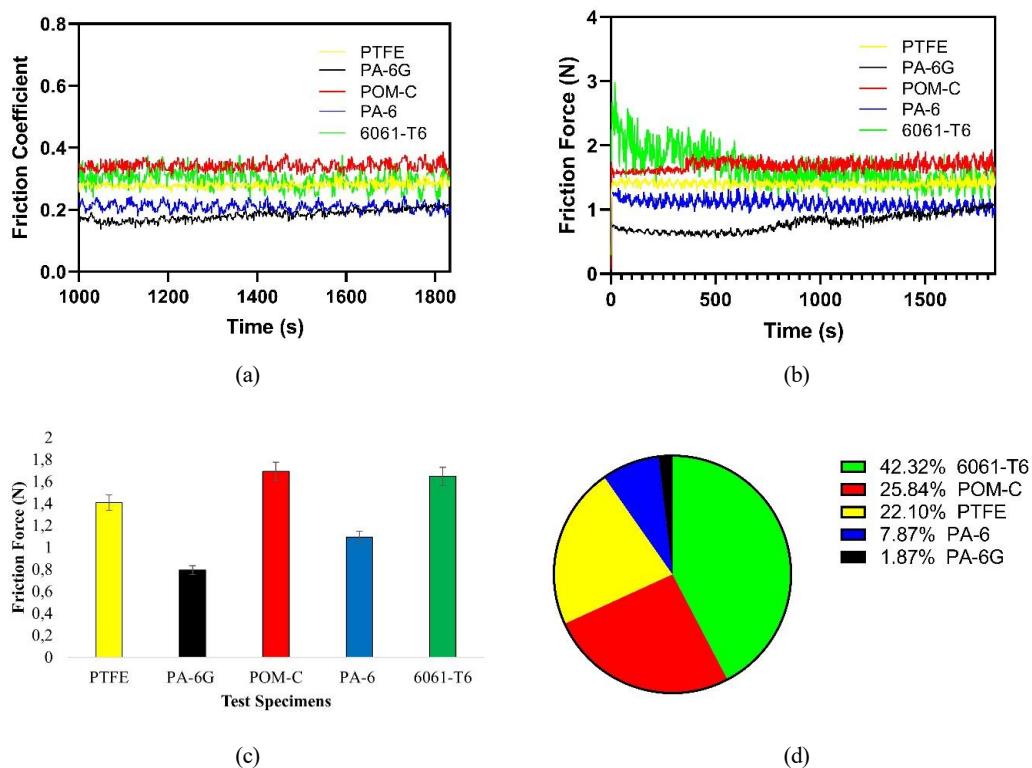

**FIGURE 4.** (a) Comparison of steady-state friction coefficients (COF). (b) Temporal variation of friction force throughout the experiments, showing the transition from initial running-in to the stabilized friction regime. (c) Mean friction forces with associated standard errors for each material combination. (d) Wear contributions of the evaluated materials.

## CONCLUSION

A comparative dry sliding wear assessment was conducted for four engineering thermoplastics POM-C, PTFE, PA-6, and PA-6G against 6061-T6 aluminum alloy under identical operational parameters. The results revealed distinct variations in tribological performance, influenced by inherent material properties, surface adaptability, and transfer film formation capacity. PA-6G demonstrated the most favorable behavior, combining a low coefficient of friction (0.16) with the smallest wear share in the total distribution (1.87%). PA-6 followed, exhibiting similarly low friction and a wear share of 7.87%, indicating its strong potential for dry, self-lubricating service conditions. PTFE presented intermediate friction values yet accounted for 22.10% of the wear share, suggesting that its low surface energy alone is insufficient to ensure minimal material loss under the given conditions. POM-C, despite its extensive industrial use, recorded the highest friction among the polymers and a wear share of 25.84%, implying the need for lubrication or surface modification in demanding dry sliding applications. The metallic counterpart, 6061-T6 aluminum alloy, displayed the largest wear share at 42.32%, underscoring the susceptibility of unlubricated metallic interfaces to significant wear accumulation. Overall, the findings establish a clear performance ranking among the tested materials under controlled conditions, filling a gap in comparative tribology literature. From a design perspective, PA-6G emerges as the most promising candidate for applications requiring low friction and minimal wear share, while POM-C and metallic surfaces may require targeted surface engineering to enhance operational longevity. These results highlight the critical role of informed material selection in ensuring mechanical system reliability and efficiency under dry contact conditions.

## ACKNOWLEDGEMENTS

The authors sincerely acknowledge the financial support from Istanbul Technical University's Scientific Research Projects Coordination Unit, which enabled this study under the conference-backed doctoral project MDK-2023-45201.

## REFERENCES

1. M. Kohutiar, L. Kakošová, M. Krbata, R. Janík, J. J. Fekiač, A. Breznická, et al., "Comprehensive review: Technological approaches, properties, and applications of pure and reinforced polyamide 6 (PA6) and polyamide 12 (PA12) composite materials," *Polymers* **17**, 442 (2025). <https://doi.org/10.3390/polym17040442>
2. M. Odrobina, T. Deák, L. Székely, T. Mankovits, R. Z. Keresztes, and G. Kalácska, "The effect of crystallinity on the toughness of cast polyamide 6 rods with different diameters," *Polymers* **12**, 293 (2020). <https://doi.org/10.3390/polym12020293>.
3. A. Altinsoy and Y. Arslan, "Investigation of the effects of deep cryogenic treatment on the structural and mechanic properties of polyoxymethylene copolymer (POM-C) materials," *Proc. Inst. Mech. Eng. Part E: J. Process Mech. Eng.* **238**, 2623–2632 (2024). <https://doi.org/10.1177/09544089221139647>
4. E. Dhanumalayan and G. M. Joshi, "Performance properties and applications of polytetrafluoroethylene (PTFE)—A review," *Adv. Compos. Hybrid Mater.* **1**, 247–268 (2018). <https://doi.org/10.1007/s42114-018-0023-8>
5. S. Unal and H. A. Tasdemir, "Tribological characterization of AlCrN, TiAlN, TiSiN and AlTiN coatings against mold steel," *Mechanics* **31**, 156–163 (2025). <https://doi.org/10.5755/j02.mech.38122>
6. Z. Rymuza, "Tribology of polymers," *Arch. Civ. Mech. Eng.* **7**, 177–184 (2007). [https://doi.org/10.1016/S1644-9665\(12\)60235-0](https://doi.org/10.1016/S1644-9665(12)60235-0)
7. S. K. Ray, A. Banerjee, B. K. Bhangi, D. Pyne, and B. Dutta, "Tribological analysis—general test standards," in *Tribology of Polymers, Polymer Composites and Polymer Nanocomposites*, 17–50 (Elsevier, 2023). <https://doi.org/10.1016/B978-0-323-90748-4.00001-7>
8. M. Oraibi Hasan, T. Khalaf Hasan, N.-S. Abdul Husain Naji, W. Ahmed Mohammed, H. Mossa Ali, H. Razzak Abbas Aljanabi, et al., "Effect of machining of aluminium alloys with emphasis on aluminium 6061 alloy – A review," *IOP Conf. Ser.: Mater. Sci. Eng.* **1107**, 012157 (2021). <https://doi.org/10.1088/1757-899X/1107/1/012157>
9. A. Kareem, J. A. Qudeiri, A. Abdudeen, T. Ahammed, and A. Ziout, "A review on AA 6061 metal matrix composites produced by stir casting," *Materials* **14**, 175 (2021). <https://doi.org/10.3390/ma14010175>
10. A. Abdelbary, *Friction and Wear of Polymer and Polymer Composites* (Springer, Singapore, 2021), pp. 33–54. [https://doi.org/10.1007/978-981-16-3903-6\\_3](https://doi.org/10.1007/978-981-16-3903-6_3)

11. W. G. Sawyer, K. D. Freudenberg, P. Bhimaraj, and L. S. Schadler, "A study on the friction and wear behavior of PTFE filled with alumina nanoparticles," *Wear* **254**, 573–580 (2003). [https://doi.org/10.1016/S0043-1648\(03\)00252-7](https://doi.org/10.1016/S0043-1648(03)00252-7)
12. P. D. Neis, N. F. Ferreira, J. C. Poletto, J. Sukumaran, M. Andó, and Y. Zhang, "Tribological behavior of polyamide-6 plastics and their potential use in industrial applications," *Wear* **376–377**, 1391–1398 (2017). <https://doi.org/10.1016/j.wear.2017.01.090>
13. R. Keresztes, M. Odrobina, R. Nagarajan, K. Subramanian, G. Kalácska, and J. Sukumaran, "Tribological characteristics of cast polyamide 6 (PA6G) matrix and their composite (PA6G SL) under normal and overload conditions using a dynamic pin-on-plate system," *Compos. Part B: Eng.* **160**, 119–130 (2019). <https://doi.org/10.1016/j.compositesb.2018.10.017>
14. Y. Sujuan and Z. Xingrong, "Tribological properties of PTFE and PTFE composites at different temperatures," *Tribol. Trans.* **57**, 382–386 (2014). <https://doi.org/10.1080/10402004.2013.812759>
15. M. S. Rahman, U. Shaislamov, J. K. Yang, J. K. Kim, Y. H. Yu, S. Choi, et al., "Effects of electron beam irradiation on tribological and physico-chemical properties of polyoxymethylene copolymer (POM-C)," *Nucl. Instrum. Methods Phys. Res. Sect. B: Beam Interact. Mater. Atoms* **387**, 54–62 (2016). <https://doi.org/10.1016/j.nimb.2016.10.001>
16. J. Li, "Friction and wear properties of PTFE composites filled with PA6," *Polym. Compos.* **31**, 38–42 (2010). <https://doi.org/10.1002/pc.20762>
17. J. Jozwik, K. Dziedzic, M. Barszcz, and M. Pashechko, "Analysis and comparative assessment of basic tribological properties of selected polymer composites," *Materials* **13**, 75 (2020). <https://doi.org/10.3390/ma13010075>
18. X. Xiong, L. Hua, X. Wan, C. Yang, C. Xie, and D. He, "Experiment and simulation of friction coefficient of polyoxymethylene," *Ind. Lubr. Tribol.* **70**, 273–281 (2018). <https://doi.org/10.1108/ILT-05-2016-0120> 19.
19. S. K. Sinha and B. J. Briscoe, *Polymer Tribology* (Imperial College Press, London, 2009). <https://doi.org/10.1142/P560>
20. G. W. Stachowiak and A. W. Batchelor, *Engineering Tribology*, 4th ed. (Butterworth-Heinemann, Oxford, 2005), pp. 1–801. <https://doi.org/10.1016/B978-0-7506-7836-0.X5000-7> 21.
21. D. Li, Y. Xie, W. Li, Y. You, and X. Deng, "Tribological and mechanical behaviors of polyamide 6/glass fiber composite filled with various solid lubricants," *Sci. World J.* **2013**, 320837 (2013). <https://doi.org/10.1155/2013/320837>
22. A. Pogačnik, A. Kupec, and M. Kalin, "Tribological properties of polyamide (PA6) in self-mated contacts and against steel as a stationary and moving body," *Wear* **378–379**, 17–26 (2017). <https://doi.org/10.1016/j.wear.2017.01.118>
23. H. Wang, X. Qi, Y. Dong, B. Fan, C. Liu, and Y. Zhang, "A formation mechanism and tribological properties of PTFE transfer film," *Research Square* (2021). <https://doi.org/10.21203/rs.3.rs-263448/v1> 24.
24. G. Kalácska, "An engineering approach to dry friction behaviour of numerous engineering plastics with respect to the mechanical properties," *Express Polym. Lett.* **7**, 199–210 (2013). <https://doi.org/10.3144/expresspolymlett.2013.18>
25. H. Endo and E. Marui, "Fundamental studies on friction and wear of engineering plastics," *Ind. Lubr. Tribol.* **56**, 283–287 (2004). <https://doi.org/10.1108/00368790410550697>